


HEAT TREATING PROGRESS

The Business and Technology of Heat Treating™

JUNE/JULY 2003

VOLUME 3 • NUMBER 4

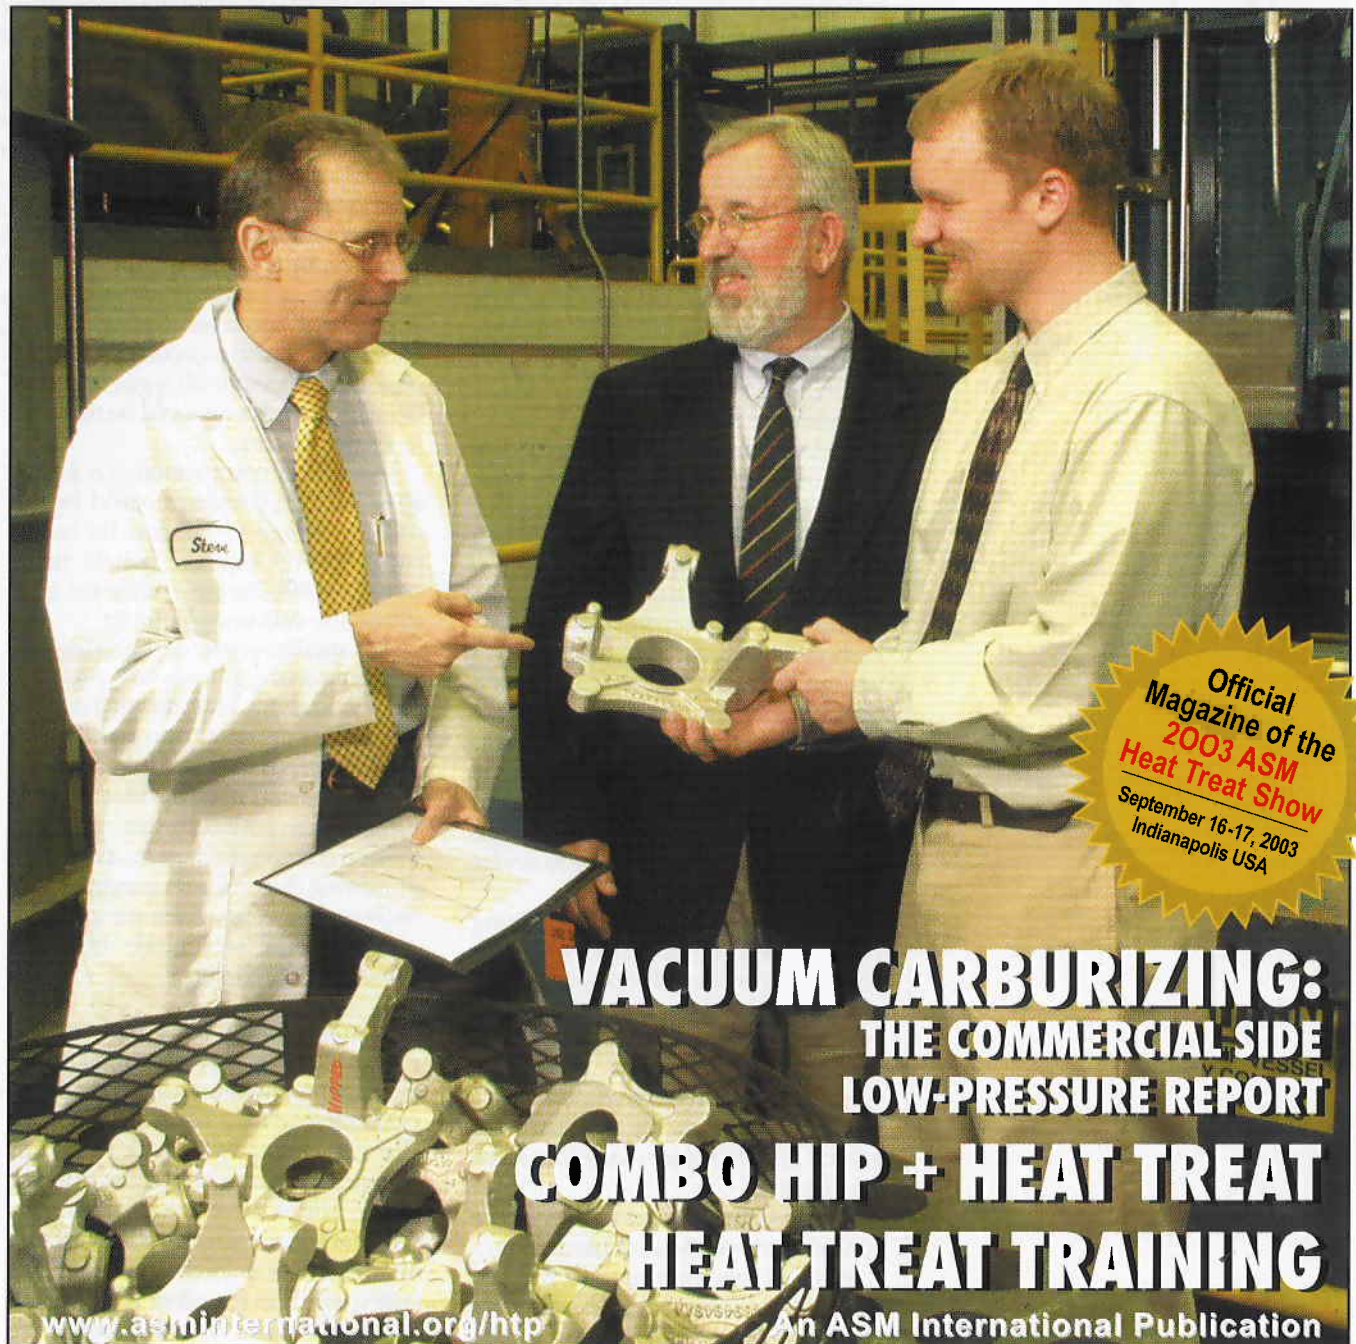

Official Magazine of the
2003 ASM Heat Treat Show
September 16-17, 2003
Indianapolis USA

**VACUUM CARBURIZING:
THE COMMERCIAL SIDE
LOW-PRESSURE REPORT**
COMBO HIP + HEAT TREAT
HEAT TREAT TRAINING

www.asminternational.org/htp

An ASM International Publication

VACUUM CARBURIZING: THE VIEW FROM A

Experimental data show that vacuum carburizing and, especially, its low-pressure variation are viable processes that job shops should consider adopting.

by Richard L. Houghton*
Hayes Heat Treating Corp.
Cranston, R.I.

Vacuum carburizing continues to gain acceptance as an alternative to atmosphere carburizing, particularly in applications where case requirements are demanding. In the United States, vacuum carburizing has predominantly been performed by captive heat treaters, where the equipment was purchased to process fairly narrow ranges of materials, part configurations, and case depths. Less common are commercial heat treaters who offer vacuum carburizing.

However, job shops should take a close look at the process, particularly in light of their customers' increasingly stringent quality demands. As this article demonstrates, former drawbacks have been overcome, resulting in a technology that is versatile, reliable, and consistent.

Advantages summarized

Carburizing in a vacuum furnace is a two-stage boost/diffusion-type process. The boost stage supplies carbon to part surfaces, which is then absorbed. The diffusion stage that follows diffuses the carbon to obtain the required case depth and surface carbon concentration. Parts are preheated in a vacuum to carburizing temperature, and then boost carburized using a hydrocarbon gas under a controlled subatmospheric pressure. The subsequent diffusion step is performed under a rough vacuum. Parts are then quenched in oil or gas under partial or positive pressure.

State-of-the-art vacuum carburizing furnace and process technology offers several important advantages:

- Uniform case microstructure, which is consistent from part to part within a load.
- Furnaces can be equipped for oil, gas, or positive-pressure quenching, which allows many materials to be processed.
- When not carburizing, the furnace can be used for vacuum hardening.
- No oxygen probes or dew-point sensors (or their maintenance) are required.

- Vacuum carburizing can be performed at temperatures from 790 to 1095°C (1450 to 2000°F). Although higher temperatures reduce cycle time, the customer must grant permission.

And, as will be shown, carburizing at lower-than-normal pressures combined with an effective preventive maintenance program can eliminate the excessive downtime that plagued older furnaces.

Sooting problem overcome

In the past, the most common vacuum carburizing problem was excessive soot formation in the furnace. This was directly attributed to the pressure used during the boost stage of carburizing and the quality of the carburizing gas. Early on, pressures as high as 400 torr were being used in combination with a circulating fan. By replacing the fan with a gas injection nozzle, the pressure could be reduced to about 200 torr.

In 1995, a comprehensive study showed that pressure could be reduced further to 100 torr by using pulse/pump injector nozzle technology.¹ Still, the downtime for soot formation was unacceptable.

The quality of the carburizing gas was then changed from 96% propane to 99% propane. This altered the composition of the soot from tar-like to a fine carbon dust that could be more easily removed from the inside of the furnace with air bake-outs.

For a commercial heat treater, better processing due to these changes in furnace carburizing pressure and gas quality translate directly into improved productivity.

Commercial shop benefited

In 1999, Hayes Heat Treating began measuring downtime for unscheduled maintenance for each of its furnaces. Our C.I. Hayes model VBQ vacuum carburizing furnace had the poorest rating. This is a two-chamber furnace, with carburizing in one chamber and an integral oil quench or partial pressure quench in the other (Fig. 1). The most common failure mode was

* Member of the ASM Heat Treating Society

COMMERCIAL SHOP

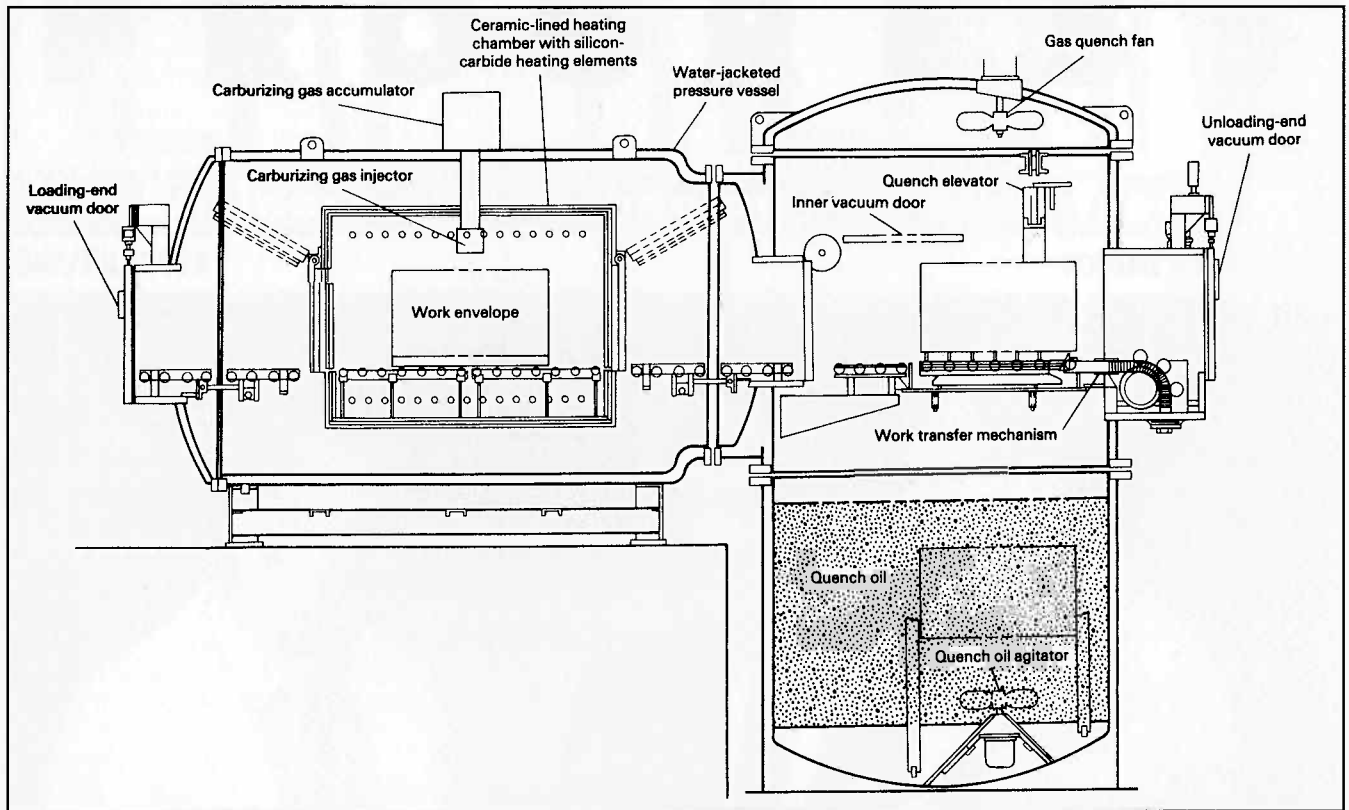


Fig. 1 — Ceramic construction furnaces are well suited for vacuum carburizing because they can be safely operated in air at process temperatures to facilitate soot removal. The Hayes VBQ furnace, for example, features silicon carbide heating elements and ceramic fiber insulation. Ref. 2.

broken heating elements due to "hot spots" caused by soot deposits.

Consequently, a project was launched with the objective of improving the availability of this furnace. As recommended, gas pressure was reduced to 100 torr from 200 torr, and gas quality was upgraded to 99% propane from 96% propane. The improvements measured each year (2000 to 2002) as a result of these two major changes, as well as from other minor enhancements, are shown in the table. These changes had no measurable effect on case hardness or case depth of carburized products.

The model VBQ furnace also is amenable to air bake-out of carbon dust. Its heating chamber features silicon carbide heating elements and ceramic fiber insulation, which can be exposed to air atmosphere at elevated temperatures.

The lesson: By focusing on process improvements and preventive main-

tenance, a vacuum carburizing furnace can be made very productive for a commercial heat treater.

Low-pressure parameters set

Back in 1994-95, experiments were conducted using standard pulse/pump parameters at pressures below 100 torr. A reduction in case depth was observed. In the past year, Hayes Heat Treating revisited this area, but using today's pulse/pump technology, propane gas, and furnace chamber pressures of 15 to 25 torr. A VBQ furnace was used.

A typical cycle for vacuum carburizing AISI 8620 steel (at 100 to 150 torr) to a case depth of 0.76 to 1.02 mm (0.030 to 0.040 in.), followed by a partial-pressure gas quench, is shown in Fig. 2. (The customer requires that parts be hardened by oil quenching in a separate operation.) This cycle for a known, repeatable production process was used as a baseline for comparing

